

Study of the copolymerization of *n*-(dichlorophenyl) maleimides with methyl methacrylate

V. B. Konsulov*, Z. S. Grozeva, J. I. Tacheva, K. D. Tachev

Faculty of Natural Sciences, Konstantin Preslavsky University of Shumen, 115 Universitetska st.,
9712 Shumen, Bulgaria

Received November 27, 2007; Revised May 22, 2008

N-(2,3-dichlorophenyl)maleimide (2,3-DCMI), N-(2,4-dichlorophenyl)maleimide (2,4-DCMI) and N-(2,6-dichlorophenyl)maleimide (2,6-DCMI) were synthesized by the reaction of maleic anhydride with 2,3-, 2,4- or 2,6-dichloroaniline in two steps. The copolymerization of 2,3-, 2,4- and 2,6-DCMI (M_1) with methylmethacrylate (MMA – M_2) was performed in 1,4-dioxane (DO) in the presence of α,α' -azobisisobutyronitrile (AIBN) as an initiator at 60°C. The monomer reactivity ratios in the copolymerization of DCMI with MMA (M_2) and Alfrey-Price $Q-e$ values were determined as follows: $r_1 = 0.16$, $r_2 = 1.97$, $Q = 0.58$, $e = 1.47$ for 2,3-DCMI-MMA; $r_1 = 0.09$, $r_2 = 2.23$, $Q = 0.55$, $e = 1.65$ for 2,4-DCMI-MMA; $r_1 = 0.04$, $r_2 = 4.19$, $Q = 0.30$, $e = 1.75$ for 2,6-DCMI-MMA. The thermostability of the resulting maleimide copolymers was investigated by thermogravimetric analysis. Effects of molecular structure of the 2,3-, 2,4- and 2,6-DCMI compounds on their copolymerization with MMA and the properties of the copolymers have been discussed.

Key words: copolymerization, N-(dichlorophenyl)maleimides, methyl methacrylate, reactivity ratios, molecular structure, thermostability.

INTRODUCTION

New functional polymers and thermostable polymeric materials, such as resistors, nonlinear optics polymer materials, membranes, sorbents, biocatalysts and other materials with medical application [1–3], have been obtained by copolymerization of N-substituted maleimides (RMI) with vinyl or methacrylic monomers. For example, poly(maleimide-co-2-ethylacrylic acid) shows curative effect on Lewis lung carcinoma [3].

There is a great interest in the investigation of copolymerization and obtaining maleimide copolymers of MMA with halogen-containing RMI [1, 2, 5–14]. It is known that on the basis of polymethylmethacrylate, the first industrial positive electron beam resistor was obtained. The sensitivity of the resistor depends on the type of the halogen atom and on the glass transition temperature (T_g) [1, 4].

Radical copolymerization of N-(4-bromophenyl) maleimide (BPMI) with MMA or 2-hydroxyethylmethacrylate (HEMA) in dioxane was investigated in [5, 6]. The structure of the methacrylate monomers affects the reactivity ratios of BPMI-MMA ($r_1 = 0.098$ and $r_2 = 1.610$) and BPMI-HEMA ($r_1 = 0.124$ and $r_2 = 1.823$). As it is shown in [5], there is a linear dependence of T_g with the increase of the

number of maleimide links in the poly(N-4-bromophenylmaleimide-co-methylmethacrylate). A linear correlation was found between the T_g values and BPMI content of the copolymers.

Janovič reported results [7] of a study of the copolymerization of N-(2,4,6-tribromophenyl)maleimide (TBMI) with methylacrylate (MA) and MMA in toluene solution. The reactivity ratios were found to be $r_1 = 0.095$ and $r_2 = 2.17$ for the system TBMI-MA and $r_1 = 0.037$ and $r_2 = 4.32$ for the system TBMI-MMA. The copolymers show a considerable enhancement of the thermal stability and a raise in the glass transition temperature upon increasing TBMI content.

The copolymerization of MMA with N-chlorophenyl maleimide (CPMI) was investigated in a number of articles [8–10]. The results show higher reactivity ratio of MMA compared to maleimide comonomers and indicate a random copolymerization. Mishra *et al.* [10] evaluated the effect of incorporation of varying molar fraction of N-(2-, 3- or 4-chlorophenyl)maleimides in the poly(methyl methacrylate) backbone on the optical, physicochemical and thermal properties of cast acrylic sheets.

Copolymers of N-(3- or 4-halogenophenyl)maleimides with ethyl and butyl methacrylates were synthesized by free-radical bulk polymerization [11–13]. The influence of UV radiation on the structure and on the thermal stability, chemical

* To whom all correspondence should be sent:
E-mail: konsulov@shu-bg.net

resistance and on some physico-mechanical properties of the copolymers was studied [11].

In a number of articles [5–14] the effect of the type of halogen atom (Cl or Br) and its position (*o*-, *m*- or *p*-) in the phenyl ring of RMI on the values of reactivity ratios (r_1 and r_2) and on the properties of maleimide copolymers was discussed. This paper reports the influence of the structure of *N*-dichlorophenyl maleimides (2,3-, 2,4- and 2,6-Cl substituents in the phenyl ring) on the copolymerization with methyl methacrylate, the reactivity ratios and the properties of the random copolymers.

EXPERIMENTAL

Materials

The monomer methyl methacrylate (Fluka AG) was distilled at a temperature of 99–100°C (MM = 100.12, $\rho = 0.943 \text{ g/cm}^3$). The maleic anhydride (Merck) was purified from maleic acid by sublimation. The 2,3-, 2,4- and 2,6-dichloroanilines (Fluka AG) were purified by vacuum distillation. The 2,2'-azobisisobutyronitrile (AIBN) was recrystallized from ethanol (m.p. 103–104°C). 1,4-dioxane (Fluka AG) was distilled over potassium hydroxide. All other reagents and solvents were of analytical purity grade (p.a.).

Synthesis and characterization of *N*-(dichlorophenyl)maleimides

N-Dichlorophenylmaleimides were prepared by reaction of maleic anhydride (MA) with 2,3-, 2,4-, and 2,6- chloroaniline, followed by cyclodehydration of the resulting maleamic acid.


Procedure for synthesis of *N*-(2,6-dichlorophenyl)maleimide. The maleimide monomer *N*-(2,6-dichlorophenyl)maleimide (2,6DCMI) was obtained from maleic anhydride (MA) and 2,6-dichloroaniline (DCA) according to the following two-step reaction procedure: 32.404 g (0.2 mol) DCA were dissolved in 40 ml of dry chloroform. The prepared solution was added to 19.612 g (0.2 mol) MA dissolved in 31 ml chloroform upon stirring continuously for 2 h in a glass reactor.

The obtained precipitate of *N*-(2,6-dichlorophenyl)maleamic acid was filtered, washed with chloroform, and dried. 26.4 g (0.1 mol) of the resulting product and 2.9 g of sodium acetate were dissolved in 40 ml of acetic anhydride and the mixture was heated at 90°C for 1 hour. The cooled down reaction mixture was poured onto 800 ml of ice water. The precipitate was filtered and the product was purified by recrystallization in ethanol-water mixture. The obtained yield was 23.5 g (89.0%). The *N*-(2,6-dichlorophenyl)maleimide is a

crystalline substance with melting point of 130–131°C.

Analysis: Calculated for $\text{C}_{10}\text{H}_5\text{O}_2\text{NCl}_2$ (242.06): C, 49.61; H, 2.08; N, 5.79; Cl, 29.29 %. Found: C, 49.55; H, 2.06; N, 5.72; Cl, 29.15%.

The molecular structure and the molecular diagram of *N*-(2,6-dichlorophenyl)maleimide are presented in the scheme:

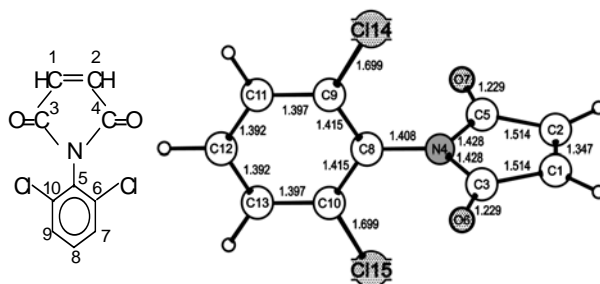

FT-IR: (cm^{-1}), 3097 and 3067 ($\nu_{\text{C-H}}$), 1776, 1715 ($\nu_{\text{C=O}}$, $\nu_{\text{C=O}}^{\text{as}}$), 1642 ($\nu_{\text{CH=CH}}$), 1584, 1488, 1433 ($\nu_{\text{C=C}}$ Ar), 1392 ($\nu_{\text{C-N}}$ Ar), 1217 ($\nu_{\text{C-O}}$), 1155 ($\nu_{\text{C-N-C}}$ MI), 1055 ($\nu_{\text{C-Cl}}$), 832 ($\gamma_{\text{C-H}}$, *cis*-MI), 804 and 715 (1,2,3-substituted phenyl), 686 (carbonyl ring deformation).

^1H NMR (CDCl_3 , TMS) δ , ppm: 7.43–7.28 (3H, Ar=C–H), 6.89 (2H, CH=CH).

^{13}C NMR (CDCl_3) δ , ppm: 168.30 (C3, C4), 134.4 (C1, C2), Aromatic carbons: 135.39 (C5), 131.16 (C6, C10), 128.51 (C7, C9) and 127.29 (C8).

The *N*-(2,3-dichlorophenyl)maleimide and *N*-(2,4-dichlorophenyl)maleimide were synthesized by a similar method.

Copolymerization

The copolymerization was performed as follows: a solution of DCMI, comonomer MMA and initiator AIBN in 1,4-dioxane as solvent were poured into a glass ampoule. The solution was degassed using dry nitrogen and the ampoule was immediately sealed and thermostated in an ultra-thermostat at $60 \pm 0.1^\circ\text{C}$. After the polymerization for a given time interval the glass ampoule was reopened and the viscous mixture was poured into ethanol. The obtained copolymers were purified twice by reprecipitation from acetone solution into ethanol. The polymers were filtered and dried in vacuum at 50°C. The composition of the obtained copolymers was calculated by elemental analysis data of nitrogen or chlorine and by ^1H NMR spectra [9, 15].

Instrumental analysis

The IR spectra were recorded on a BOMEM Michelson 100 FTIR spectrometer using KBr pellets or on Specord 75 IR instrument using suspension in nujol or polymer films. The ^1H and ^{13}C NMR

presence of maleimide monomeric units was proved by the resonance signals at 7.76, 7.51, and 7.32 ppm for the aromatic protons. The signals between 3.64–3.72 ppm were assigned to the protons of the –OCH₃ group in MMA units, while the triplet centered at 1.21 ppm was attributed to the protons of the –CH₃ groups. To the protons of –CH₂– were assigned signals at 1.71–2.15 ppm, and the signals of methyne protons –CH– appeared at 2.86 and 2.94 ppm.

The ¹³C NMR spectrum of the poly(*N*-2,6-dichlorophenylmaleimide-co-methyl methacrylate) containing 39.5 mol% maleimide units is shown in Fig. 1. The signals at 175.3–177.8 ppm characterize the maleimide carbonyl groups, these at 173.2–174.2 ppm – the ester carbonyl groups. The carbon atoms in the aromatic ring give resonance signals at 127.9, 128.6, 131.3, 134.1, 134.3, and 134.6 ppm. The MMA-units are characterized by: 15.0–19.1 ppm α-methyl groups; 51.8–55.7 ppm –OCH₃ ester groups.

The copolymer compositions were determined by elemental analysis (Table 2) and by ¹H NMR [9, 15], based on the intensity of the aromatic protons

signals (3H, at about 7.32–7.76 ppm) from maleimides and the intensity of MMA proton signal (3H, at about 3.64–3.72 ppm). The mole fraction of DCMI (*m*₁) in the copolymers was calculated according to the following equation:

$$m_1 = \frac{I_1}{(I_1 + I_2)}, \quad (1)$$

where *I*₁ and *I*₂ represent the integrated area intensities of the aromatic protons in DCMI and of the methoxy protons in MMA respectively. These results were correlated with experimental data for the copolymer composition, obtained by elemental analysis (Table 3).

Reactivity ratios. Effect of the molecular structure of *N*-dichlorophenylmaleimides

To determine the reactivity ratios of the monomers *r*₁ (2,3-, 2,4-, or 2,6-DCPMI) and *r*₂ (MMA) the copolymerization of the comonomers with a conversion degree up to 15–20 % has been studied. Some of the obtained results are represented in Table 3.

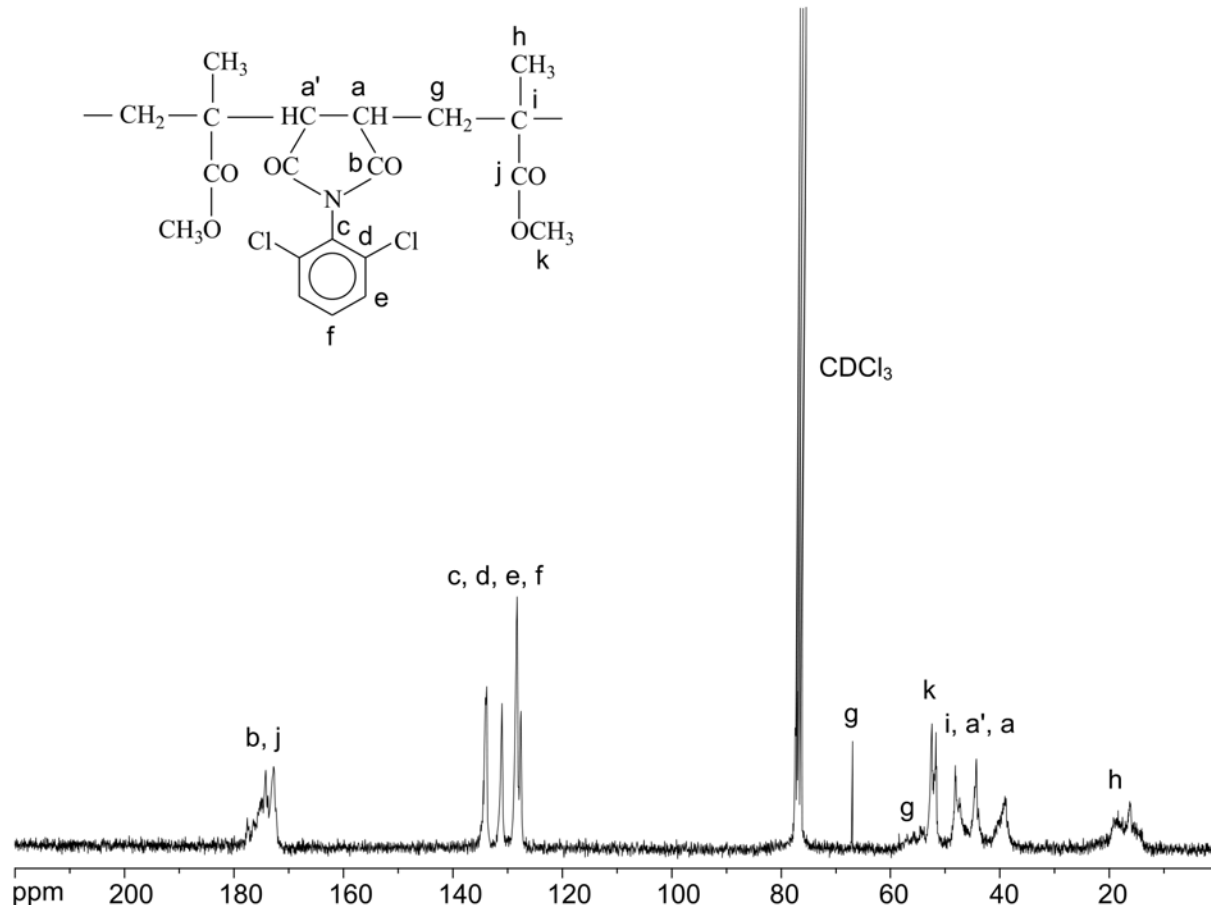


Fig. 1. ¹³C NMR spectrum of poly[(*N*-2,6-dichlorophenyl) maleimide-co-methyl methacrylate] containing 39.5 mol.% *N*-(2,6-dichlorophenyl)maleimide.

Table 3. Copolymerization of N-dichlorophenylmaleimides (M_1) with methyl methacrylate (M_2) in dioxane solution at different monomer feed ratios ($C_M = 1.0$ mol/l, $T = 60^\circ\text{C}$).

Sample number	DCMI (M_1) in monomer feed		Conversion, %	Polymerization rate, R_p %/min	Fraction of DCMI (M_1) in copolymer (mol.%)		$[\eta]^*$ dl/g
	mol. %				N	$^1\text{H NMR}$	
1	2,3-DCMI	20.0	15.4	0.15	9.9	9.6	0.32
2		50.0	17.5	0.18	27.4	27.9	0.23
3		79.8	15.7	0.14	54.1	54.6	0.18
4	2,4-DCMI	20.5	17.1	0.12	9.5	9.3	0.29
5		50.0	18.0	0.13	26.5	26.6	0.24
6		79.8	16.8	0.11	48.5	48.9	0.11
7	2,6-DCMI	20.0	16.5	0.13	9.3	9.2	0.25
8		48.7	18.9	0.23	14.7	14.8	0.21
9		79.8	15.4	0.10	39.5	40.0	0.20

* η determined in 1,4-Dioxane at 25°C ($d_k = 0.54$ mm, Ubbelohde).

The experimental data showed that the copolymerization rate (R_p) depends only slightly on the content of DCMI in the monomer feed. A weak kinetic maximum, shifted from the equimolar composition, was observed at higher MMA content (66–75 mol.%). This is characteristic of monomer systems with weak electron donor or electron acceptor interactions [1, 7, 16].

The monomer reactivity ratios for the copolymerization of DCMI with MMA were determined based on the monomer feed ratios and the copolymer composition by Kelen-Tüdös (KT) method [17–18]. The dependence of the obtained copolymer composition (m_2) upon monomer feed composition ($M_2 = \text{MMA}$) according to experimental data from three series of experiments is represented in Fig. 2. The dependence curves show that the copolymerization of all the three monomer pairs lead to obtaining random copolymers. In the resulting copolymers the number of MMA units prevails over the maleimide units (see also Table 2).

The r_2 values for MMA are higher ($r_2 > 1$) than the r_1 values for the maleimides ($r_1 \ll 1$) for the three monomer systems (Table 4). The connection between the structure of the monomer and its reactivity in free-radical reactions is controlled by resonance, polar and steric factors. The Q-e scheme gives a quantitative evaluation of the role of resonance and polar effects. The Q_1 and e_1 values of N-(2,3-, 2,4- and 2,6-dichlorophenyl)maleimides were calculated using the Alfrey-Price Q-e scheme [19, 21] based on the reactivity ratios:

$$e_1 = e_2 \pm (-\ln r_1 r_2)^{0.5} \quad (2)$$

$$Q_1 = \frac{Q_2}{r_2} \exp[-e_2(e_2 - e_1)] \quad (3)$$

Values of $Q_2 = 0.74$ and $e_2 = 0.40$ for MMA were used for this purpose according to the literature data [7, 15].

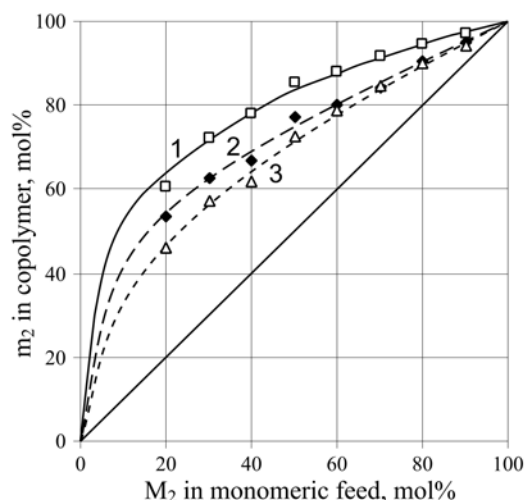


Fig. 2. Monomer-copolymer composition curves for the copolymerization of methyl methacrylate (M_2) with M_1 : N-(2,6-dichlorophenyl)maleimide (curve 1), N-(2,4-dichlorophenyl)maleimide (curve 2) or N-(2,3-dichlorophenyl)maleimide (curve 3).

Table 4. Monomer reactivity ratios r_1 , r_2 and Q - e values for copolymerization of N-dichlorophenyl maleimides (M_1) with methyl methacrylate (M_2).

M_1	r_1	r_2	$1/r_1$	$1/r_2$	$r_1 r_2$	Q_1	e_1
2,3-DCMI	0.16 ± 0.02	1.97 ± 0.08	6.2	0.51	0.315	0.58	1.47
2,4-DCMI	0.09 ± 0.03	2.23 ± 0.11	11.1	0.45	0.200	0.55	1.65
2,6-DCMI	0.04 ± 0.01	4.19 ± 0.09	25.6	0.24	0.168	0.30	1.75

The resonance effect influences the reactivity of the monomer and its radical. The conjugation in the MMA molecule determines the high reactivity of the monomer, while the activity of its radical is lower. Although MMA is 1,1-disubstituted monomer, the steric factor does not affect its polymerization ability [19]. One can conclude in view of the r -values that the reactivity of the N-dichlorophenyl maleimides decreases, when the second Cl-atom is located at a greater distance from the first one (at *ortho*-position in the aromatic ring). The reactivity ratios decrease in the following order: 2,3-DCMI > 2,4-DCMI > 2,6-DCMI. A possible explanation of these observations could be connected with the influence of the induction effect (I-effect > M-effect for Cl-atom) on the electron acceptor properties of the functional $-\text{CH}=\text{CH}-$ group of the maleimide ring resulting in a decrease of the donor-acceptor interactions with the weak donor monomer MMA [7]. The 2,6-DCMI is about 25 times more active with respect to MMA radical in the reaction

of cross propagation. ($1/r_1 = k_{12}/k_{11} \sim 25$). The ortho steric effect has a weaker influence on 2,3- and 2,4-DCMI as they have asymmetric structure. These monomers are about 6 and 11 times more active to MMA-radical, respectively.

The reactivity ratios show that the two macroradicals in the examined systems have higher activity to methacrylic monomer and the obtained copolymers are enriched in MMA-units. The MMA has high polymerization activity in the reaction of homo and cross propagation [7, 11]. The reaction of homopropagation occurs at higher rate ($k_{22} > k_{21}$) and as a result in the polymer chain the number of consecutive MMA units alternate ($r_1, r_2 < 1$) the maleimide link or diads [5, 6, 11]. Therefore, the distribution of the monomeric links and the design of the macromolecules of the three copolymers of MMA with 2,3-, 2,4-, and 2,6-DCMI would differ. They would depend also on the monomer ratio DCMI/MMA, at which the maleimide copolymer is obtained (see Table 3, Fig. 2).

Copolymer microstructure

The microstructure in the resulting copolymers was determined using the monomer reactivity ratios. The placement probabilities P_{11} , P_{12} , P_{21} and P_{22} and the mean sequences length μ_1 (DCMI) and μ_2 (MMA) were calculated using the equations in references [21, 22]. The values of P_{11} , P_{12} , P_{21} , P_{22} , μ_1 and μ_2 are represented in Table 5.

Table 5. Data for the structure of copolymers of *N*-dichlorophenylmaleimide (M_1) with methylmethacrylate (M_2).

Type of DCMI	Sample	P_{11}	P_{12}	P_{21}	P_{22}	Mean sequence length	
						μ_1	μ_2
2,3-DCMI	1	0.0385	0.9615	0.1126	0.8874	1.04	8.89
	2	0.1379	0.8621	0.3367	0.6633	1.16	2.97
	3	0.3872	0.6128	0.6672	0.3328	1.63	1.50
2,4-DCMI	4	0.0227	0.9773	0.1037	0.8963	1.02	9.65
	5	0.0825	0.9174	0.3300	0.6700	1.09	3.23
	6	0.2627	0.7373	0.6394	0.3606	1.36	1.56
2,6-DCMI	7	0.0099	0.9901	0.0563	0.9437	1.01	17.76
	8	0.0366	0.9634	0.1847	0.8153	1.04	5.19
	9	0.1365	0.8635	0.4853	0.5147	1.16	2.06

The obtained data show that the probability of formation of maleimide diads (P_{11}) is low and it depends on the mole fraction DCMI in the monomer feed. The mean sequence length μ_1 values increase from 1.04 to 1.63 in the 2,3-DCMI/MMA system,

from 1.02 to 1.36 in the 2,4-DCMI/MMA system and from 1.01 to 1.16 in the 2,6-DCMI/MMA system. The P_{21} values are higher than P_{11} and increase with the concentration of maleimide monomers. For all studied comonomer ratios the probabilities P_{12} and P_{22} are higher than P_{11} and P_{21} . This implies that in maleimide copolymers, diads, triads and even much longer sequences of MMA units are formed. The μ_2 values increase from 1.50 to 8.9 in the 2,3-DCMI/MMA system; from 1.56 to 9.65 in the 2,4-DCMI/MMA system and from 2.06 to 17.76 in the 2,6-DCMI/MMA system.

Thermostability of the copolymers of DCMI with MMA

The thermal properties of copolymers DCMI with MMA were determined by TGA in static air atmosphere. Data at the temperature of the initial weight loss [5, 7, 12] of a sample (T_i), the temperature at 50% weight loss (T_{50}), the temperature of maximum decomposition rate (T_{max}) and final decomposition temperature (T_f), as well as the percentage of the weight loss of the samples at 350°C and 500°C are summarized in Table 6 and shown in Figure 3.

Table 6. Thermal properties of copolymers of *N*-(dichlorophenyl)maleimides with methylmethacrylate (heating rate 7°C/min in static air atmosphere).

Copolymer sample	T_i , °C	T_{50} , °C	T_{max} , °C	T_f , °C	Percentage weight loss at		Residue at T_f , %
					350°C	500°C	
1	316	373	378	530	28	93	7
4	320	365	370	500	33	99	1
7	325	375	380	520	16	98	2

The copolymer samples were stable up to 316°C for 2,3-DCMI-MMA, up to 320°C for 2,4-DCMI-MMA and up to 328°C for 2,6-DCMI-MMA. All the samples showed a single step decomposition in the temperature region 280–420°C, which corresponds to random main chain scission of MMA-MMA links (335–427°C) of PMMA. The maximum values of the weight loss (decomposition) are at about 370–380°C. In the case of 2,3-DCMI-MMA copolymer, the weight loss up to 350°C was 28%, that of 2,4-DCMI-MMA – 33%, and that of 2,6-DCMI-MMA – 16%. The percentage of char yield increased upon increasing DCMI content in the maleimide copolymers.

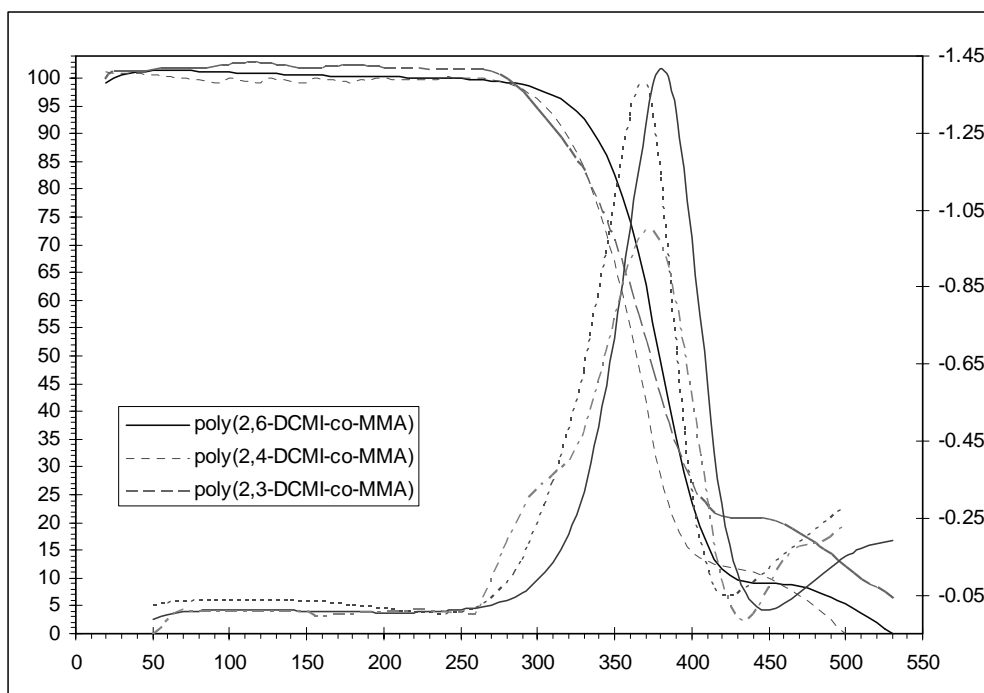


Fig. 3. TG and DTG trace of poly(2,6-DCMI-co-MMA), poly(2,4-DCMI-co-MMA) and poly(2,3-DCMI-co-MMA) in air atmosphere (heating rate 10°C/min).

CONCLUSIONS

By the radical copolymerization of *N*-(2,3-dichlorophenyl)maleimide, *N*-(2,4-dichlorophenyl)maleimide, and *N*-(2,6-dichlorophenyl)maleimide with methyl methacrylate random maleimide copolymers have been obtained. The monomer reactivity ratios of *N*-dichlorophenylmaleimides r_1 (0.18, 0.09 and 0.04 for 2,3-, 2,4-, and 2,6-DCMI respectively) revealed the effect of molecular structure of *N*-substituted maleimides on their copolymerization with methyl methacrylate and on the properties of the obtained maleimide copolymers. The thermostability of the studied maleimide copolymers was about 80–90°C higher compared to polymethylmethacrylate. The role of the position of Cl-atoms in the phenyl ring of *N*-dichlorophenylmaleimides for the thermal properties of the copolymers was insignificant. Their thermostability increased with the molar fraction of *N*-dichlorophenyl maleimide units in the macromolecules.

REFERENCES

- V. B. Konsulov, in: *Polymeric Materials Encyclopedia: Maleimide copolymers (N-substituted)*, vol. 6, J. C. Salamone (Ed.), CRC Press Boca Raton, New York, 1996, p.3996.
- Tz. Godjevargova, R. Nenkova, V. Konsulov, *J. Mol. Catal. B: Enzym.*, **38**, 59 (2006).
- Z. Zhu, L. Shi, J. Huang, *Bioorg. Med. Chem. Lett.*, **12**, 2843 (2002).
- B. M. Gong, J. C. W. Chien, *J. Polym. Sci. Part A: Polym. Chem.*, **27**, 1149 (1989).
- J. Borbely, T. Kelen, V. Konsulov, Z. Grozeva, *Polymer Bull.*, **26**, 253 (1991).
- V. Konsulov, Z. Grozeva, *Bulg. Chem. Commun.*, **31**, 38 (1999).
- Z. Janovič, T. Matusinovič, F. Ranogajec, *Makromol. Chem.*, **194**, 1915 (1993).
- A. Kumar, *J. Macromol. Sci.*, **A24**, 711 (1987).
- V. Choudhary, A. Mishra, *J. Appl. Polym. Sci.*, **62**, 707 (1996).
- A. Mishra, T. J. M. Sinha, V. Choudhary, *J. Appl. Polym. Sci.*, **68**, 527 (1998).
- A. Rytzel, *J. Appl. Polym. Sci.*, **74**, 2924 (1999).
- A. Rytzel, *J. Appl. Polym. Sci.*, **81**, 3244 (2001).
- H. Naguib, G. Saad, M. Elsabeé, *Polym. Int.*, **52**, 1217 (2003).
- V. Konsulov, Z. Grozeva, T. Kelen, J. Borbely, *Makromol. Chem.*, **193**, 847 (1992).
- A. O. Kress, L. J. Mathias, G. Cei, *Macromolecules*, **22**, 537 (1989).
- C. P. Yang, S. S. Wang, *J. Polym. Sci. Part A: Polym. Chem.*, **27**, 15 (1989).
- T. Kelen, F. Tüdös, *J. Macromol. Sci.-Chem.*, **A9**, 1 (1975).
- T. Kelen, F. Tüdös, B. Turcsanyi, *Polym. Bull.*, **2**, 71 (1980).
- G. E. Ham (ed) in: *Copolymerization*, Khimia, Moscow, 1971, pp. 65–81.
- G. S. Georgiev, V. P. Zubov, *Eur. Polym. J.*, **14**, 93 (1978).
- S. Morariu, C. Hulubei, *High Perform. Polym.*, **18**, 185 (2006).
- V. Konsulov, D. Dyakova, A. Lyapova, Z. Grozeva, *Bulg. Chem. Commun.*, **39**, 72 (2007).

ИЗСЛЕДВАНЕ НА СЪПОЛИМЕРИЗАЦИЯТА НА N-(ДИХЛОРОФЕНИЛ)МАЛЕИМИДИ С МЕТИЛМЕТАКРИЛАТ

В. Б. Консулов*, З. С. Грозева, Й. И. Тачева, К. Д. Тачев

*Факултет по природни науки, Шуменски университет „Епископ Константин Преславски“,
Ул. „ Университетска“ № 115, 9712 Шумен*

Постъпила на 27 ноември 2007 г.; Преработена на 22 май 2008 г.

N-(2,3-дихлорофенил)малеимид (2,3-ДХМИ), N-(2,4-дихлорофенил)малеимид (2,4-ДХМИ), N-(2,6-дихлорофенил)малеимид (2,6-ДХМИ) са синтезирани чрез взаимодействие на малеинов анхидрид с 2,3-, 2,4- или 2,6-дихлороанилин в два стадия. Съполимеризацията на 2,3-, 2,4- и 2,6-ДХМИ (M_1) с метилметакрилат (ММА- M_2) е проведена в 1,4-диоксан (ДО) в присъствие на α, α' -азобисизобутиронитрил като инициатор при 60°C. Определени са константите на съполимеризация и Q-e стойностите: $r_1 = 0.16$, $r_2 = 1.97$, $Q = 0.58$, $e = 1.47$ за 2,3-ДХМИ-ММА; $r_1 = 0.09$, $r_2 = 2.23$, $Q = 0.55$, $e = 1.65$ за 2,4-ДХМИ-ММА; $r_1 = 0.04$, $r_2 = 4.19$, $Q = 0.30$, $e = 1.75$ за 2,6-ДХМИ-ММА. Термостабилността на получените малеимидни съполимери е изследвана чрез термогравиметричен анализ. Дискутира се влиянието на молекулната структура на 2,3-, 2,4- и 2,6-ДХМИ върху съполимеризацията им с ММА и свойствата на получените съполимери.